

ForTii[®] Ace MX53

PPA–GF50

50% Glass Fiber Reinforced, PA4T, Heat Stabilized, for Automotive applications

Print Date: 2026–05–23

ForTii[®] Ace MX53 is a PPA with unique fatigue performance and chemical resistance. The high aromatic content and high Tg lead to excellent part stiffness and low creep, even up to 150°C. Moisture uptake occurs slowly with very limited impact on dimensions.

PROPERTIES	TYPICAL DATA	UNIT	TEST METHOD
RHEOLOGICAL PROPERTIES			
	DRY / COND		
Molding shrinkage (parallel)	0.35 / *	%	ISO 294–4
Molding shrinkage (normal)	0.9 / *	%	ISO 294–4
MECHANICAL PROPERTIES			
	DRY / COND		
Tensile modulus	18000 / 18900	MPa	ISO 527–1/–2
Tensile modulus (–40°C)	18500 / –	MPa	ISO 527–1/–2
Tensile modulus (40°C)	17500 / 17500	MPa	ISO 527–1/–2
Tensile modulus (80°C)	17300 / 16000	MPa	ISO 527–1/–2
Tensile modulus (100°C)	17000 / 11000	MPa	ISO 527–1/–2
Tensile modulus (120°C)	16000 / –	MPa	ISO 527–1/–2
Tensile modulus (150°C)	11500	MPa	ISO 527–1/–2
Tensile modulus (160°C)	10000	MPa	ISO 527–1/–2
Tensile modulus (180°C)	8000	MPa	ISO 527–1/–2
Tensile modulus (200°C)	7200	MPa	ISO 527–1/–2
Stress at break	260 / 250	MPa	ISO 527–1/–2
Stress at break (–40°C)	300 / –	MPa	ISO 527–1/–2
Stress at break (40°C)	235 / 220	MPa	ISO 527–1/–2
Stress at break (80°C)	205 / 160	MPa	ISO 527–1/–2
Stress at break (100°C)	190 / 125	MPa	ISO 527–1/–2
Stress at break (120°C)	170 / –	MPa	ISO 527–1/–2

Seller represents and warrants exclusively that on the date of delivery by Seller the product shall be in conformity with the specifications agreed upon. Seller makes no other representations or warranties, whether express or implied. Seller is not responsible or liable for the design of the products of the Customer and it is the responsibility of the Customer to determine that the Seller's product is safe, complies with application laws and regulations, and is technically or otherwise fit for its intended use. Seller does not endorse or claim suitability of its products for a specific application and disclaims each and every representation or warranty, whether express or implied, in that respect. Typical values are indicative only and are not to be construed as being binding specifications. Colorants in the product or other additives may cause significant variations in typical values. Copyright © Envalior 2026. All rights reserved. No part of the information may be reproduced, distributed, or transmitted in any form or by any means, including photocopying, recording, or other electronic or mechanical methods, without the prior written permission of Envalior.

Property Data

ForTii[®] Ace MX53

Print Date: 2026-05-23

<i>PROPERTIES</i>	<i>TYPICAL DATA</i>	<i>UNIT</i>	<i>TEST METHOD</i>
Stress at break (150°C)	130	MPa	ISO 527-1/-2
Stress at break (160°C)	120	MPa	ISO 527-1/-2
Stress at break (180°C)	100	MPa	ISO 527-1/-2
Stress at break (200°C)	85	MPa	ISO 527-1/-2
Strain at break	2.1 / 2	%	ISO 527-1/-2
Strain at break (-40°C)	2.3 / -	%	ISO 527-1/-2
Strain at break (40°C)	2 / 2	%	ISO 527-1/-2
Strain at break (80°C)	2 / 2.6	%	ISO 527-1/-2
Strain at break (100°C)	2.05 / 3.4	%	ISO 527-1/-2
Strain at break (120°C)	2.1 / -	%	ISO 527-1/-2
Strain at break (150°C)	3.4	%	ISO 527-1/-2
Strain at break (160°C)	4.1	%	ISO 527-1/-2
Strain at break (180°C)	4.9	%	ISO 527-1/-2
Strain at break (200°C)	5	%	ISO 527-1/-2
Flexural modulus	17000 / 17800	MPa	ISO 178
Flexural strength	380 / 360	MPa	ISO 178
Flexural modulus (120°C)	15700	MPa	ISO 178
Flexural modulus (160°C)	10000	MPa	ISO 178
Flexural modulus (180°C)	8000	MPa	ISO 178
Flexural modulus (200°C)	7400	MPa	ISO 178
Charpy impact strength (+23°C)	80 / 75	kJ/m ²	ISO 179/1eU
Charpy impact strength (-30°C)	70 / 65	kJ/m ²	ISO 179/1eU
Charpy notched impact strength (+23°C)	12 / 11	kJ/m ²	ISO 179/1eA
Charpy notched impact strength (-30°C)	12 / 11	kJ/m ²	ISO 179/1eA
<i>THERMAL PROPERTIES</i>		<i>DRY / COND</i>	
Melting temperature (10°C/min)	335 / *	°C	ISO 11357-1/-3
Temp. of deflection under load (1.80 MPa)	320 / *	°C	ISO 75-1/-2
Coeff. of linear therm. expansion (parallel)	0.15 / *	E-4/°C	ISO 11359-1/-2

Seller represents and warrants exclusively that on the date of delivery by Seller the product shall be in conformity with the specifications agreed upon. Seller makes no other representations or warranties, whether express or implied. Seller is not responsible or liable for the design of the products of the Customer and it is the responsibility of the Customer to determine that the Seller's product is safe, complies with application laws and regulations, and is technically or otherwise fit for its intended use. Seller does not endorse or claim suitability of its products for a specific application and disclaims each and every representation or warranty, whether express or implied, in that respect. Typical values are indicative only and are not to be construed as being binding specifications. Colorants in the product or other additives may cause significant variations in typical values. Copyright © Envalior 2026. All rights reserved. No part of the information may be reproduced, distributed, or transmitted in any form or by any means, including photocopying, recording, or other electronic or mechanical methods, without the prior written permission of Envalior.

Property Data

ForTii[®] Ace MX53

Print Date: 2026-05-23


PROPERTIES	TYPICAL DATA	UNIT	TEST METHOD
Coeff. of linear therm. expansion (normal)	0.5 / *	E-4/°C	ISO 11359-1/-2
Coeff. of linear therm. expansion (parallel)	0.27	E-4/°C	ASTM D696
Coeff. of linear therm. expansion (normal)	0.3	E-4/°C	ASTM D696
Burning Behav. at 3.0 mm nom. thickn.	HB / *	class	IEC 60695-11-10
Thickness tested	HB / *	mm	IEC 60695-11-10
UL recognition	3 / *	—	—
Thermal Index 5000 hrs	188	°C	IEC 60216/ISO 527-1/-2

OTHER PROPERTIES

DRY / COND

Humidity absorption	1.4 / *	%	Sim. to ISO 62
Density	1660 / —	kg/m ³	ISO 1183

Tens. fatigue 8Hz, T, R=0.1,
dry

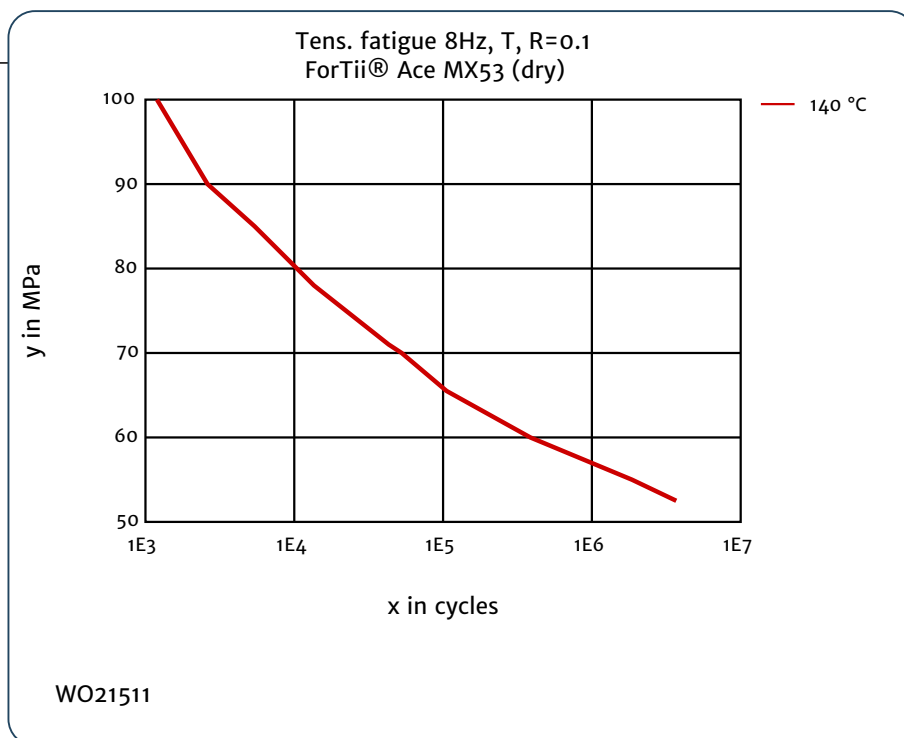

Seller represents and warrants exclusively that on the date of delivery by Seller the product shall be in conformity with the specifications agreed upon. Seller makes no other representations or warranties, whether express or implied. Seller is not responsible or liable for the design of the products of the Customer and it is the responsibility of the Customer to determine that the Seller's product is safe, complies with application laws and regulations, and is technically or otherwise fit for its intended use. Seller does not endorse or claim suitability of its products for a specific application and disclaims each and every representation or warranty, whether express or implied, in that respect. Typical values are indicative only and are not to be construed as being binding specifications. Colorants in the product or other additives may cause significant variations in typical values. Copyright © Envalior 2026. All rights reserved. No part of the information may be reproduced, distributed, or transmitted in any form or by any means, including photocopying, recording, or other electronic or mechanical methods, without the prior written permission of Envalior.